

Research Article

Effect on Poly(C₆H₅NH₂) Emeraldine Salt by FeCl₃ and KMnO₄ as Secondary Dopants

Kedir Mamma, Khalid Siraj* and Nathan Meka

Department of Chemistry, College of Natural Sciences, Jimma University, P. O. Box 378,
Jimma, Ethiopia

Abstract

Polyaniline in its emeraldine salt form was synthesized by chemical method from aniline monomer in the presence of HCl mixed with LiCl and Ammonium-persulphate (APS) as oxidant. Then a portion of samples was de-doped with NH₃ solution and another equal portion was separately post doped with secondary dopants such as FeCl₃ and KMnO₄ respectively. Finally the dried samples of polyaniline prepared in all its three different forms were characterized by ultraviolet – visible (UV-Vis) spectroscopy, Fourier- Transform Infrared (FTIR) spectroscopy and electrical conductivity measurement. FT-IR and UV-Vis spectra confirmed the expected structural modification upon doping, undoping and post doping processes of the polymer. The influences of secondary doping on the electrical conductivity were also investigated from their spectroscopic data and the dramatic rise in conductivity was said to be induced from the secondary doping is attributed by structural rearrangement from a compact-coil form of PANI to a more expanded conformation. The result also shows that secondary doping increased the π conjugation. Their measured electrical conductivities were from 0.02 for undoped, 156 for primary doped form and increasing from 158 to 210 S/cm for those secondary doped polyaniline.

Keywords: Secondary dopant; PANI; FT-IR; UV-Visible; Electrical conductivity

Peer Reviewers: Jianping Xu, PhD, Associate Professor, Department of Polymer Science and Engineering, Zhejiang University; Taihong Shi, PhD, Department of Environment Science, Sun Yat-sen University, China

Received: March 12, 2013; **Accepted:** May 10, 2013; **Published:** May 25, 2013

Competing Interests: The authors have declared that no competing interests exist.

Copyright: 2013 Siraj K *et al.* This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

***Correspondence to:** Khalid Siraj, Department of Chemistry, College of Natural Sciences, Jimma University, P. O. Box 378, Jimma, Ethiopia. E-mail: chemdocprof@gmail.com

Introduction

Conductive polymers are peculiar in nature that they conduct current without having a

partially empty or partially filled band. The conjugation arising from chemical unsaturation of the carbon atom in conducting polymers is the main cause for charge transport. The presence of localized electronic

states of energies less than the band gap arising due to the changes in the local bond order have attributed to the possibility of new types of charge conduction phenomenon in these conjugated polymers [1].

Polyaniline (PANI) has been investigated extensively for over 100 years, has attracted special interest as a conducting material, and become the most prominent subject of study. Such popularity, in both theoretical and practical aspects, is a consequence of its unique properties: existence of various oxidation states, electrical and optical activity, low cost monomer, the polymerization reaction is straightforward and proceeds with high yield. PANI has an excellent environmental stability [2].

A first fairly detailed description of this product which was earlier known as ‘aniline black’ was provided by Green and Woodhead

[3]. The later discoveries on polyaniline dealt with its electrical conductivity and other properties like electrochemical redox activity, reversible doping/dedoping, electrochromism etc. [4] These diverse and important features seem to be promising in wide area of practical applications in rechargeable power sources, sensors, magnetic shielding, electrochemical capacitors, electro-chromic devices, corrosion protection etc. Further attention has been focused on PANI due to two prime reasons: (i) It can be synthesized easily both by electrochemical and chemical oxidation processes and (ii) it shows a particular sensitivity to the proton activity of its environment [5].

In reality; “polyaniline” is a name for whole family of polymers, which can be described by the formula presented in Figure 1.

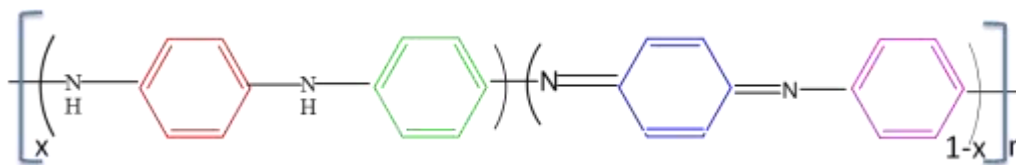


Figure 1 General formula for different forms of polyaniline base

Correctness of the formula presented above was proved, among others, by spectroscopic studies of Wudl and co-workers [6, 7]. Green and Woodhead were the first to depict PANI as a chain of aniline molecules coupled head-to-tail at the para position of the aromatic ring. They have proposed a linear octameric structure for PANI [8, 9].

Polyaniline, a typical phenylene based polymer, has a chemically flexible $-NH-$ group in the polymer chain flanked by phenyl rings on either sides. The diversity in physicochemical properties of polyaniline is

traced to the $-NH-$ group. The difference in the composition of amine and imine segments of polyaniline generates several oxidation states of this material ranging from completely reduced leucoemeraldine to completely oxidized pernigraniline states. The different forms of polyaniline can be readily converted to one another by simple redox methods. Out of several possible oxidation states, the 50 % oxidized emeraldine salt state shows electrical conductivity [6].

Polyaniline is unique among inherently conducting polymers in that it can be rapidly

converted between base and salt forms by treatment with acid or base. These reversible redox and pH switching properties together with the electrical conductivity of its emeraldine salt form, its ease and cheapness of synthesis, and its good environmental stability, have led to its becoming the most extensively studied conducting organic polymer over the past decade, and a wide range of potential applications are currently being developed [10].

Polyaniline has an electronic conduction mechanism that seems to be unique among conducting polymers, because it is doped by protonation as well as undergoing the p-type doping [11, 12]. This results in the formation of a nitrogen base salt rather than the carbonium ion of other p-doped polymers [13]. Many of the unusual properties of polyaniline were resulted because of the A-B nature of the polymer configuration, whereas most other conducting polymers are of the A-A type. Furthermore, the B component is the basic N heteroatom, which is involved with the conjugation in polyaniline more than the heteroatoms in similar polymers such as polypyrrole (PPY) [13]. Therefore, the conductivity of PANI depends on both the oxidation state of the polymer and its degree of protonation.

Among the various oxidation states of the PANI its “emeraldine” form can be doped to the highly conducting state. It consists of amine ($-NH-$) and imine ($=N-$) sites in equal proportions. The imine sites are protonated by acids HA to the bipolaron (dication salt) form. However, this undergoes a further rearrangement to form the delocalized polaron lattice, which is a polysemiquinone radical-cation salt. Although theoretical calculations have predicted that the bipolaron state is energetically more favored than the polaron

[13], it is widely agreed that polarons are the charge carriers responsible for the high conductivity in polyaniline [14-18]. It has been proposed that the presence of coulombic interactions, dielectric screening and local disorder in the polyaniline lattice act to stabilize the delocalized polaron state. It has also been shown that bipolaron states do exist in polyaniline, but they are few in number and are not associated with the conducting regions of the polymer [18, 19].

The study of conducting polymers received a major wave of momentum in the 1990s when Heeger et al. discovered secondary-doping effects in PANI systems [20, 21]. Their studies showed that exposure of camphor sulfonic-acid-doped PANI to m-cresol can increase the conductivity of the original polymer from $1-2 \text{ Scm}^{-1}$ to nearly 400 Scm^{-1} . Given the ability to dramatically improve PANI's conductivity, these solvents were commonly termed as ‘secondary dopants’ for PANI [22].

Recently, much interest has been shown in enhancing the order and consequent conducting properties of conducting polyaniline salts via post-polymerization treatment with an appropriate “secondary dopant”. In particular, much attention has focused on the influence of m-cresol solvent or vapor on the properties of the emeraldine salt PANI. (+)-HCSA obtained by doping emeraldine base (EB) with racemic (+)-10-camphorsulfonic acid [23-26].

The conductivity of PANI-HA emeraldine salts is dependent on the temperature as well as humidity and hence, polymer water content [27, 28]. In general, attachment of functional groups decreases the conductivity, whereas the formation of copolymers between aniline and functionalized aniline results in polymers with intermediate conductivity. In addition, the preparation conditions [29, 30], particularly as

they relate to the formation of structural defects [31] and the polymer morphology [32, 33], influence conductivity. It has also been reported that the conductivity of PANI is dependent on the solvent it is cast from or exposed to. This phenomenon has been referred to as “secondary doping” [34, 35]. The solvent causes a change in the polymer conformation that result in increased conductivity.

Materials and Methods

All the chemicals used in this work were of Analytical grade. Aniline, $C_6H_5NH_2$ (99.5%, Aldrich), was purified by double distillation under vacuum and stored in a refrigerator and Ammonium persulphate, $(NH_4)_2S_2O_8$ (98%, Technopharmchem, was stored in a refrigerator and used as supplied) whereas N-methylpyrrolidinone (NMP) (99.5%, Aldrich), Acetone ($\geq 99.9\%$, Aldrich), Methanol, CH_3OH (Anhydrous, 99.8%, Aldrich), Ammonia solution, NH_3 (27%, Merck), Hydrochloric acid, HCl (37%, Fluka), Lithium chloride, $LiCl$ (anhydrous, $\geq 99.0\%$, Ubichem) and Sulfuric acid, H_2SO_4 (95-98%, Fluka) used as supplied.

Sample preparation

Polyaniline hydrochloride (PANI-ES) sample was chemically synthesized by following standard procedure for the polymerization of aniline by using aniline, ammonium peroxydisulfate (APS), and the appropriate dopant (HCl , contains dissolved $LiCl$). More precisely, a doubly distilled 0.20M aniline was dissolved in to 100 mL volumetric flask containing acidic solution of (1.0 M HCl , 5.0 M $LiCl$) prepared in de-ionized water. The

solution was stirred for 1 hr in the plastic beaker and a resulted color less solution cooled to $-20^\circ C$ for 30 minutes. Then the solution was transferred to 500 mL round bottom flask located in the reaction setup that maintained at $0^\circ C$ in ice bath and 0.25M Ammonium peroxydisulfate (APS) was added slowly (1ml drop/min) above the solution. Then mixtures were stirred for 5 hours at a temperature maintained between $0-2^\circ C$ and $pH = 0-1$ after that the mixture was left for polymerization room temperature for 48 hrs. After 48 hrs the resulting dark green PANI precipitate was collected on a filter, washed with distilled water, again with three 100 mL portions of 0.2M HCl and similarly with acetone. Polyaniline (emeraldine) hydrochloride powder was dried in air and then in oven at $60^\circ C$ for 3 and 5 hrs respectively. Finally, the dried powder of PANI-ES was grinded to fine powders and preserved for undoping and secondary doping sample preparations.

Doping and De-doping (Insulating) in Polyaniline

ES- powder of polyaniline was dissolved in the concentrated 4.0 M H_2SO_4 in the crucible glass and stayed on post doping for 72 hrs at room temperature and then heated in the oven at $60^\circ C$ for additional 72 hrs. Finally, the green color fine powder were obtained and preserved for sample analysis. To prepare an insulated polyaniline of (PANI-EB) 0.2 g dry ES was dumped into 1.0 M NH_4OH solution (at $pH = 8-9$) and stirred for 4 hrs. The resulting blue color PANI precipitate was collected on a filter, washed with distilled water, again with methanol. Polyaniline (emeraldine base) powder was dried in vacuum then in air.

Secondary doping of polyaniline with salts of transition metals

Anhydrous FeCl_3 (0.1625 g, 1.0 mM) was dried in high vacuum at 30 °C for 3 hours. Dry FeCl_3 was dissolved in acidic methanol solution (pH~1). Polyaniline -ES (0.200 g) powder was mixed with dopant solution and stirred for 2 hrs. The doped mixture was kept for 15 hrs at room temperature in the glass crucible and dried in the oven at 60°C for 5 hrs. Finally, the green-blue powders of polyaniline was formed and then the dried redoped polyaniline powders were grind to fine powders and preserved for sample preparations. 0.158 g anhydrous KMnO_4 separately dissolved in the small volume of concentrated sulfuric acid solution (pH< 1) and then follow the same procedure adopted with FeCl_3 .

Characterizations of polyaniline

The synthesized samples of polyaniline were characterized by UV-Vis spectroscopy and FT-IR spectroscopy. FT-IR spectra were recorded using Thermo Nicolet V-200 FTIR spectrometer by KBr pellet method in the region 400 to 4000 cm^{-1} . Optical absorption spectrum was taken using a double beam spectrometer (T80 UV/VIS, PG Instruments, Ltd.) and sample holder quartz glass with wave length scanned between 190nm-1100nm.

Conductivity measurements

Electrical conductivity was measured by using

the digital multimeter with lead metal roads inserting in the solutions and also using pH-ISE by Conductivity Meter model-250. Then, the current-voltage (I-V) measurements were obtained using the two-point probe method and resistivity measurements were carried out.

Results and Discussion

UV-Vis spectra for undoped polyaniline (PANI-EB)

UV-Vis spectra of black color undoped polyaniline (PANI-EB) powder in solvent NMP turns to bright blue color solution has two absorption peaks at 328 and 630 nm. The absorption at 328 nm has been suggested to arise from excitation of the benzene segment including amine structures in polyaniline, whereas the peak at 630 nm arises from the quinoid structure including imines [5].

On the other hand the UV-Vis spectra (Figure 2) of PANI doped with 1.0M HCl in solvent NMP has two absorption peaks at 430 and 850 nm. This is attributed when the nitrogen atoms in imine groups are protonated; nitrogen and its neighboring quinoid ring become a semiquinoid radical cation, generation of these two absorption peaks due to the presence of polaron/bipolaron band transition [6, 7]. Decreasing of undoped polyaniline absorption in the 630 nm is proportional to increasing of doped polyaniline absorption in the 850 nm.

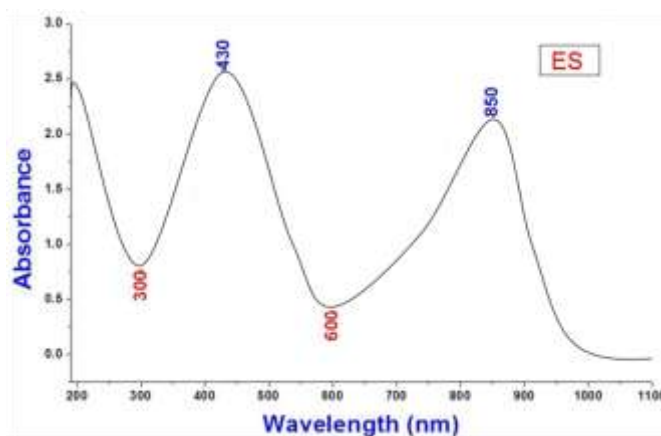


Figure 2 UV-Vis Spectra of Polyaniline-HCl (PANI-ES) in the NMP solution

At high protonation level 630 nm band completely disappears. Therefore, adding acidic solution NMP into polyaniline solution, both 330 nm ($\pi_B - \pi^*$) and 630 nm ($\pi_B - \pi_Q$) absorptions decrease in intensities. Simultaneously, two new absorptions appear at 430 and 850 nm, which are attributed to polarons/bipolarons in protonated polyaniline [8].

UV-Vis spectra of secondary doped polyaniline with salts of transition metals

Polyaniline complexation with salts of

transition metals was manifested by a green-blue coloration of the reaction medium. Again the UV-Vis spectra of polyaniline secondary doped with salts of transition metals (Figures 3, 4) also indicate almost similar to the ES form of polyaniline. Thus when transition metal salts are mixed with polyaniline they undergo complex formations as PANI-Cl-Mⁿ⁺ (where Mⁿ⁺ is the transition metal ions) in the same way as PANI-ES complexed with FeCl₃ presented in Figure 5.

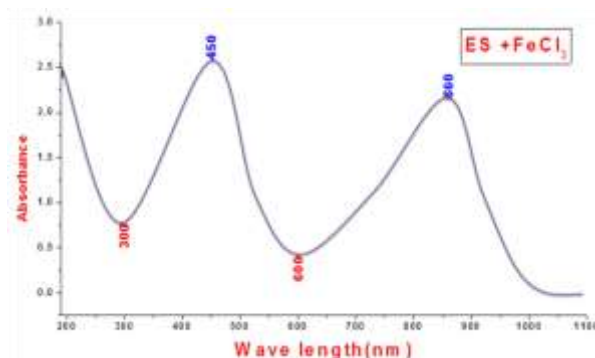
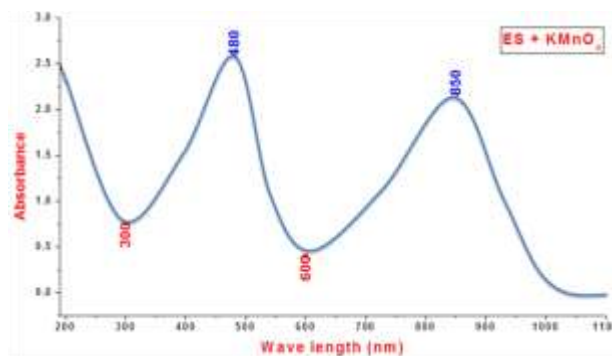
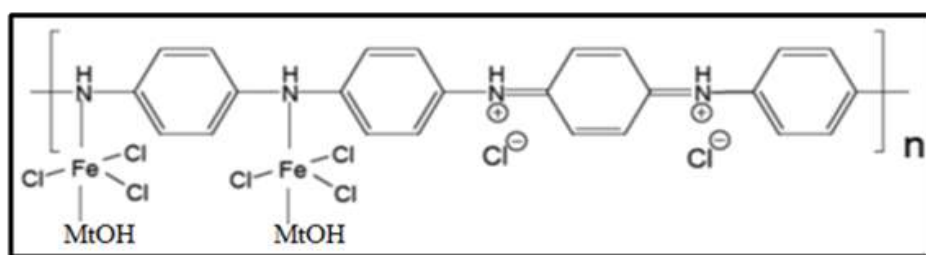


Figure 3 UV – Vis spectra of PANI secondary doped with FeCl₃

Figure 4 UV-Vis spectra of PANI secondary doped with KMnO_4 Figure 5 PANI-ES re-doped with FeCl_3 in the acidic methanol solution (MtOH)

On the other hand, there was a slight improvement in the conductivities of polyaniline re-doped with those transition metals salts this is also expects from the post modification process might improve the deformed structure of PANI – ES due to an ion of those salts substitute on the phenyl ring. In the same way their solubility's were also highly improved in the most organic solvents like Chloroform, NMP, DMSO as compared

with ES this is also attributed to the effects of post modification by the secondary doping process. Expected electronic change in all prepared samples of PANI can be mathematically explained by calculating the band gaps from their UV-Vis spectra. The energy $h\nu$ of the photon is related to the wavelength λ of UV-Vis radiation by the following relation [36-38].

$$\Delta E = h\nu = E(\text{LUMO}) - E(\text{HOMO}) = \frac{1.24}{\lambda(\mu\text{m})} \text{ eV} \quad \text{--- 1}$$

Where h is Planck's constant ν frequency of light and c velocity of light. The calculated

band gap for each case is reported in (Table 1).

Table 1 Conductivity and computed energy gap of the undoped and primary and secondary doped polyaniline samples.

Dopants	Conductivity (S/cm)	HOMO-LUMO (Energy gap), eV
Polyaniline undoped	0.02	2.45
Polyaniline doped with HCl, ES	156	2.34
ES - FeCl ₃	168	2.12
ES - KMnO ₄	210	1.97

Infrared (IR) Spectroscopy of polyaniline

IR studies were carried out in order to confirm the presence of lithium chloride in the polyaniline/ pre-doping polyaniline and post-doping with different dopants. The powder samples of undoped polyaniline were dissolved in NMP and the rest primary and secondary samples were dissolved in chloroform to record the spectra. For PANI, it is most useful for obtaining qualitative information regarding the average oxidation states. IR spectroscopy can distinguish between benzenoid rings and quinoid rings in

the 1300 to 1600 cm⁻¹ region of the spectrum; this region of the spectrum is most useful for distinguishing between oxidation states in the undoped polymer, as the quinoid stretches disappear on doping.

Figure 6, shows comparative IR spectras of PANI along with doped by secondary dopants as recorded through spectrometer. Our results show that no pronounced peaks have been observed in the spectra region 1750 – 2750 cm⁻¹, but there is a shift in the responses after doping the samples with HCl and LiCl as a primary dopant and re-doping this samples with FeCl₃ and KMnO₄ as a secondary dopants separately.

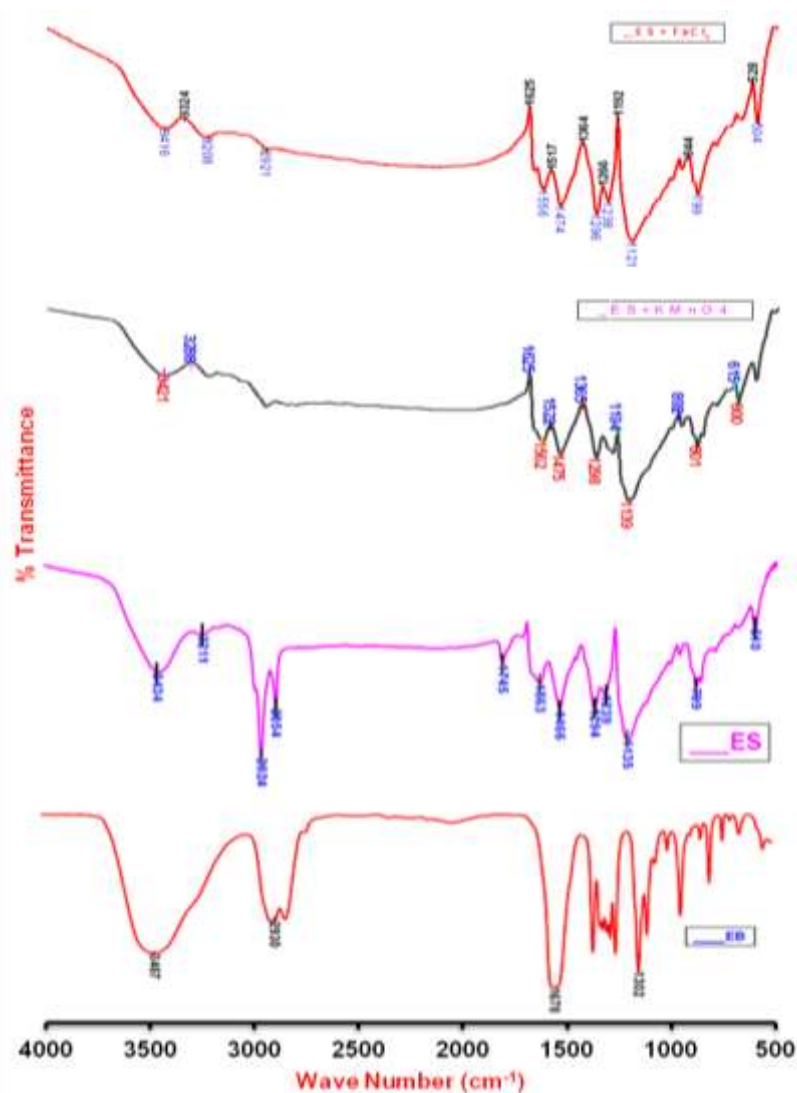


Figure 6 FTIR of Undoped, primary doped PANI- HCl (ES), secondary doped with FeCl_3 and KMnO_4

Giving rise to a good comparison between the doped and undoped polymer, the medium intensity band at 1591 cm^{-1} (as in undoped PANI) is assigned to the C–N stretching of secondary aromatic amine, which shifts to 1518 cm^{-1} in doped samples. The band at $\sim 616\text{ cm}^{-1}$ observed for undoped and doped PANI samples is the characteristic peak of C–H out of plane bending vibration of benzene ring. The medium band observed (in doped samples) around 1586 cm^{-1} is the characteristic peak of nitrogen quinoid ring

and is absent in polyaniline undoped sample. The vibration band at 616 cm^{-1} is assigned to the benzene ring distribution, whose intensity increases with increase in dopants.

IR spectra of emeraldine salt re-doped with the salts of transition metal (Figure 6) shows almost the same spectra as ES especially with FeCl_3 due to the same Cl^- group as HCl doped ES but for the case of Mn^{7+} there are additional peaks nearly at 600 which are expected to be the presence of MnO_4^- ions.

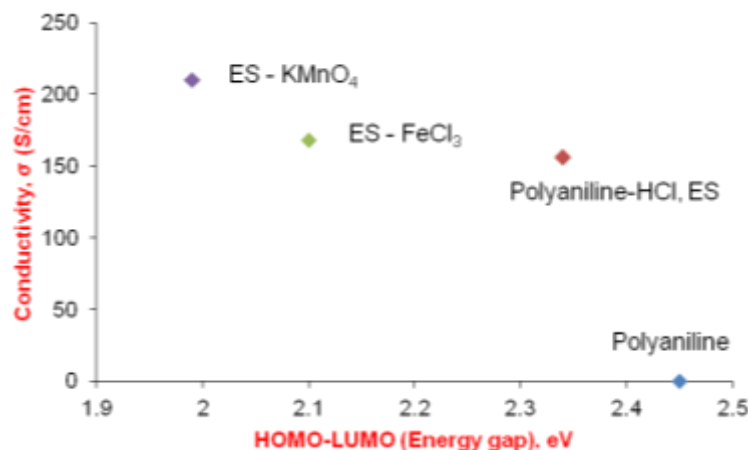


Figure 7 Conductivity versus HOMO-LUMO gap plot of the PANI-ES samples with different dopants.

Conclusion

The dramatically rise in conductivity was said to be induced from the secondary doping is attributed by structural rearrangement from a compact-coil form of PANI to a more expanded conformation. Therefore it is possible to conclude that secondary doping increased the π conjugation. The most direct proof should be the characteristic absorption peak of π conjugation bonds of the EB- of PANI after de-doping of both FeCl_3 and KMnO_4 secondary doped ES, so as to cancel the effect of different kinds of doping acids. It can be seen that absorption peak of conjugated structure of EB- of PANI chains becomes widened and red-shifted significantly. This fact directly demonstrates that secondary doping enhances the π conjugation structure of PANI in the composite.

Acknowledgement

We are thankful to the Department of Chemistry, College of Natural Science, Jimma University, Ethiopia for providing necessary facilities for carrying out this research.

References

1. Rao PS, Sathyanarayana DN, Jeevananda T. In *Advanced Functional Molecules and Polymers*, H. S. Nalwa (ed.), **Gordon and Breach**, Tokyo, 2001, 3:79
2. Waltman RJ, Bargon J and Diaz AF. Electrochemical studies of some conducting polythiophene films. *J Phy Chem.* 1983, 87:1459-1463
3. Jansson R, Arwin H, Bjorklund A, Lunstrom I. Characterization and switching of thin poly-N- methylpyrrole films. *Thin Solid Films*, 1980, 125: 205-211
4. Diaz AF, Matninez A, Kanazawa KK, Salmon M. Electrochemistry of some substituted pyrroles. *J Electroanal Chem.* 1980, 130:181-187
5. Ohsawa JJ, Kaneto K, Yoshino K. Electrical and Optical Properties of Electrochemically Prepared Polyfuran. *Jpn J Appl Phys.* 1984, 23:L663-L665
6. Huang WS, Humphrey BD, MacDiarmid AG. Polyaniline, a novel conducting polymer. Morphology and chemistry of its oxidation and reduction in aqueous electrolytes, *J Chem Soc Faraday Trans 1.* 1986, 82:2385-2400

7. Lu FL, Wudl F, Nowak M, Heeger AJ. Phenyl-capped octaaniline (COA): an excellent model for polyaniline, *J Am Chem Soc.* 1986, 108:8311-8313
8. Green AG, Woodhead AE. CCXLIII.—Aniline-black and allied compounds. Part I, *J Chem Soc Trans.* 1910, 97:2388-2403; CXVII.—Aniline-black and allied compounds. Part II, 1912, 101:1117-1123
9. Athawale AA, Kulkarni MV, Chabukswar VV. Studies on chemically synthesized soluble acrylic acid doped polyaniline, *Mat Chem Phys.* 2002, 73:106-110
10. MacDiarmid AG, Chiang JC, Richter AF, Somasiri NLD, Epstein AJ. In *Conducting Polymers*, L. Alcacer, ed., **Reidel Publication**, Dordrecht, 1987, 105
11. Avlyanov JK, Min YG, MacDiarmid AG, and Epstein AJ. Polyaniline – conformational-changes induced in solution by variation of solvent and doping level. *Synth Met* 1995, 72: 65-71
12. Min Y, Xia Y, MacDiarmid AG, and Epstein AJ. Vapor phase “secondary doping” of polyaniline. *Synth Met.* 1995, 69:159-160
13. Cao Y, Smith P, Heeger AJ. Counter-ion induced processibility of conducting polyaniline and of conducting blends of polyaniline in bulk polymers. *Synth Met.* 1992, 48:91-97
14. Rao PS, Sathyanarayana DN, Jeevananda T. In *Advanced Functional Molecules and Polymers: Electronic and Photonic Properties*, H. S. Nalwa (ed.), **Gordon and Breach**, Tokyo, 2001, 3: 79-95
15. MacDiarmid AG Epstein AJ. The concept of secondary doping as applied to polyaniline. *Synth. Met.* 1994, 65:103-116
16. Ball IJ, Huang SC, Wolf RA, Shimano JY, Kaner RB. Pervaporation studies with polyaniline membranes and blends. *J Mem Sci.* 2000, 174:161-176
17. Jonsson SKM, Birgersson J, Crispin X, et al. The effects of solvents on the morphology and sheet resistance in poly (3, 4-ethylenedioxythiophene)– polystyrenesulfonic acid (PEDOT–PSS) films. *Synth Met.* 2003, 139:1-10
18. Bredas JL, Chance RR, Silbey R. Comparative theoretical study of the doping of conjugated polymers: Polarons in polyacetylene and polyparaphenylene. *Phys Rev B.* 1982, 26:5843-5854
19. Angelopoulos M, Asturias GE, Ermer SP, Scherr EM, MacDiarmid AG, Akhtar M, Kiss Z, Epstein AJ. Polyaniline: Solutions, Films and Oxidation State. *Mol Cryst Liq Cryst.* 1988, 160:151-163
20. Epstein AJ, Ginder JM, Zuo F, Biegelow RE, Wou HS, Tanner DB, Fichter AF, Huang WS, MacDiarmid AG. Insulator-to-metal transition in polyaniline. *Synth Met.* 1987, 18:303-309.
21. Wei Y, Jang GW, Chan CC, Hsueh KF, Hariharan R, Patel SA, Whitecar CK. Polymerization of aniline and alkyl ring-substituted anilines in the presence of aromatic additives. *J Phys Chem.* 1990, 94:7716-7721
22. MacDiarmid AG, Chiang JC, Richter AF, Somarisi NLD. In *Conducting Polymers, Special Applications*. L. Alcacer (Ed). Reidel, Dordrecht, 1987,105
23. Mattoso LHC, MacDiarmid AG, Epstein AJ. Controlled synthesis of high molecular weight polyaniline and poly(o-methoxyaniline). *Synth Met.* 1994, 68:1-11
24. Heeger AJ. Semiconducting and Metallic Polymers: The Fourth Generation of Polymeric Materials. *Angew Chem In. Ed.* 2001, 40:2591-2611
25. Beadle PM, Nicolau YF, Banka E, Rannou P, Djurado D. Controlled polymerization of

- aniline at sub-zero temperatures. **Synth Met.** 1998, 95:29
26. Jiang Y, Li D, Xie D, Wu Z, Yang B. **Proceedings of SPIE-The International Society for Optical Engineering** 2001, 4414:358-361
 27. Nakajima T, Kawagoe T. Polyaniline: Structural analysis and application for battery. **Synth Met.** 1989, 28:629-638
 28. Watanabe A, Mori K, Mikuni M, Nakamura Y, Matsuda M. Comparative study of redox reactions of polyaniline films in aqueous and nonaqueous solutions. **Macromolecules.** 1989, 22:3323-3327
 29. Fosong W, Jinsong T, Lixiang W, Hongfang Z, Zhishen M. Study on the Crystallinity of Polyaniline. **Mol Cryst Liq Cryst.** 1988, 160:175-184
 30. Pron A, Genoud F, Menardo C, Nechschein M. The effect of the oxidation conditions on the chemical polymerization of polyaniline. **Synth Met.** 1988, 24:193-201
 31. Thyssen A, Borgerding A, Schiltze JW. Formation and electronic conductivity of polyaniline. **Makromol Chem Macromol Symp.** 1987, 8:143-157
 32. Schacklette LW, Baughman RH. Defect Generation and Charge Transport in Polyaniline. **Mol Cryst Liq Cryst.** 1990, 189:193-212
 33. Ryu KS, Moon BW, Joo J, Chang SH. Characterization of highly conducting lithium salt doped polyaniline films prepared from polymer solution. **Polymer.** 2001, 42:9355-9360
 34. MacDiarmid AG, Epstein AJ. Secondary doping in polyaniline. **Synth Met.** 1995, 69:85-92.
 35. Tanaka J, Mashita N, Mizoguchi J, Kume, K. Molecular and electronic structures of doped polyaniline. **Synth. Met.** 1989, 29:175-184
 36. Conklin, JA, Huang, SC, Huang, SM, Wen, T, Kaner, RB. Thermal Properties of Polyaniline and Poly(aniline-co-o-ethylaniline). **Macromolecules** 1995, 28:6522-6527
 37. Kaner RB, MacDiarmid AG. Plastics that conduct electricity. **Scientific America.** 1988, 34:60-65
 38. Alexander M, Dubois P. Polymer-layered silicate nanocomposites: preparation, properties and uses of a new class of materials. **Materials Science and Engineering: R: Reports.** 2000, 28:1-63
 39. Kargirwar SR, Thakare SR, Choudhary MD, Kondawar SB, Dhakate SR. Morphology and electrical conductivity of self-doping polyanilines synthesized via self-assembly process. **Adv Mat Lett** 2011, 2: 397-401.
 40. Scrosati B eds. *Application of electroactive polymers.* **Chapman and Hall**, London, UK, 1993
 41. Dimitriev OP, Smertenko PS, Stiller B, Brehmer L. Polyaniline-transition metal salt complexes: insight into formation mechanisms. **Synth Met.** 2005, 149:187-192
 42. Catedral MD, Tapia AKG, Sarmago RV. Effect of Dopant Ions on the Electrical Conductivity and Microstructure of Polyaniline (Emeraldine Salt). **Science Diliman.** 2004, 16:41-46
 43. Ravikiran YT, Lagare MT, Sairam M, Mallikarjuna NN, Sreedhar B, Manohar S, MacDiarmid AG. Synthesis, characterization and low frequency AC conduction of polyaniline/niobium pentoxide composites, **Synth Met.** 2006, 156:1139-1147
 44. Chandrakanthl N, Careem MA. Thermal stability of polyaniline. **Polymer Bulletin.** 2000, 44:101-108